

Non-Zhang-Rice singlet character of the first ionization state of T-CuO

Clemens P. J. Adolphs,¹ Simon Moser,^{2,3} George A. Sawatzky,^{1,4} and Mona Berciu^{1,4}

¹*Department of Physics and Astronomy, University of British Columbia, Vancouver, British Columbia, Canada, V6T 1Z1*

²*Institute of Condensed Matter Physics, Ecole Polytechnique Fédérale de Lausanne, CH-1015 Lausanne, Switzerland*

³*Advanced Light Source, Berkeley, California 94720, USA*

⁴*Quantum Matter Institute, University of British Columbia, Vancouver, British Columbia, Canada, V6T 1Z4*

(Dated: February 4, 2016)

We argue that tetragonal CuO (T-CuO) has the potential to finally settle long-standing modelling issues for cuprate physics. We compare the one-hole quasiparticle (qp) dispersion of T-CuO to that of cuprates, in the framework of the strongly-correlated ($U_{dd} \rightarrow \infty$) limit of the three-band Emery model. Unlike in CuO₂, magnetic frustration in T-CuO breaks the C_4 rotational symmetry and leads to strong deviations from the Zhang-Rice singlet picture in parts of the reciprocal space. Our results are consistent with angle-resolved photoemission spectroscopy data but in sharp contradiction to those of a one-band model previously suggested for them. These differences identify T-CuO as an ideal material to test a variety of scenarios proposed for explaining cuprate phenomenology.

PACS numbers: 74.72.Gh, 74.25.Jb, 74.20.Pq

Introduction: Understanding the high-temperature superconductivity in cuprates [1] is one of the biggest challenges in condensed matter physics. These layered materials contain two-dimensional (2D) CuO₂ layers which exhibit antiferromagnetic (AFM) order when undoped, and host superconductivity upon doping. Consequently, it is widely believed that understanding the behaviour of a doped CuO₂ layer is the key to understand the unusual properties of these materials.

The first step is to understand the nature of the quasiparticle (qp) that forms when a hole is doped into a CuO₂ layer. Despite many efforts, this issue is not yet settled.

The Cu $3d_{x^2-y^2}$ and ligand O $2p$ are the most relevant orbitals, and their appropriate model is the three-band Emery Hamiltonian [2]. Zhang and Rice argued that its quasiparticle is a Zhang-Rice singlet (ZRS) hopping on the Cu sublattice, well described by the (relatively) simpler one-band t - J or Hubbard Hamiltonians [3–5]. Significant effort focusing on these one-band models followed. In the absence of exact solutions or accurate approximations, progress came from numerical studies of finite-size clusters and from Cluster Dynamical Mean-Field Theory [6]. These showed that the qp dispersion is strongly influenced by the quantum fluctuations of the AFM background [7], and that longer-range hopping is necessary for quantitative agreement with experimental measurements [8–11]. The longer-range hoppings required to achieve this agreement agree with those calculated theoretically [12, 13]. This was taken as proof that these extended one-band models are correct, and the focus shifted to studying them at finite doping [14]. While much work was done in the past two decades, the lack even of consensus that they support robust, high-temperature superconductivity raises doubts about how appropriate they are to describe the hole-doped cuprates [15].

There are two reasons why one-band models might fail to capture the desired physics at finite doping: (i) they may describe the qp correctly yet fail to appropriately model the effective interactions between qps , responsible

for pairing. This was shown to occur when degrees of freedom from different sublattices are mapped onto an effective one-band model [16]. Because in cuprates the doped holes reside on oxygen whereas the magnons reside on Cu [17], a one-band model may similarly fail to mimic their full interaction; (ii) they may predict the correct qp dispersion for the wrong reasons. Support for the latter view comes from our recent work on the $U_{dd} \rightarrow \infty$ limit of the Emery model; the resulting Hamiltonian has spins at the Cu sites and doped holes on the O sublattice [17]. In stark contrast to one-band models where spin fluctuations are key to obtaining the correct qp dispersion, here this is found even in their absence [18]. This qualitative difference shows that although these qps have similar dispersion, it is controlled by different physics [19].

To fully decide whether these one- and three-band models are equivalent, one must compare them for a material like CuO₂, so that it is described by similar Hamiltonians, however one where they give different predictions. In this Letter we show that tetragonal CuO (T-CuO) is precisely this material whose investigation can finally resolve these fundamental modeling issues.

Thin films of T-CuO were recently grown epitaxially on SrTiO₃ [20]. They consist of stacks of weakly-interacting CuO layers, whose structure has two intercalated CuO₂ lattices (sharing the same O), see Fig. 1(a). Fig. 1(b) shows a CuO₂ layer. Because Cu $3d_{x^2-y^2}$ orbitals only hybridize with their ligand O $2p$ orbitals, shown in the same color in Fig. 1, the two CuO₂ sublattices would be effectively decoupled if pp hopping between the two sets of O $2p$ orbitals was absent [21]. In this case, a hole doped into one sublattice would evolve just like in a CuO₂ layer, and the same (but doubly-degenerate) qp dispersion would be predicted by both one- and three-band models, as discussed.

However, the CuO₂ sublattices are coupled by pp hopping, which lifts this degeneracy. The resulting qp dispersion was measured by angle resolved photoemission spectroscopy (ARPES) [22]. It seems to be quite similar

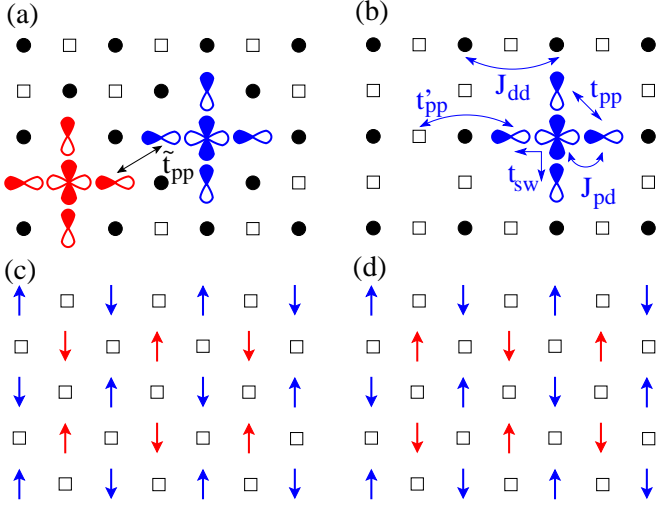


FIG. 1. (color online) Structure of a layer of (a) T-CuO, and (b) CuO₂. Full circles are Cu, empty squares are O. The Cu $3d_{x^2-y^2}$ orbitals are drawn at a few sites, with white/dark lobes showing our choice for positive/negative signs. The corresponding ligand O $2p$ orbitals are also indicated on neighboring O sites. The T-CuO layer can be thought of as two intercalated CuO₂ layers sharing common O. The coppers of the two sublattices hybridize with different O $2p$ orbitals. Panels (c) and (d) show the two degenerate ground-states of the undoped T-CuO layer. Different colors are used for the Cu spins on the two sublattices for better visibility.

to that of CuO₂ and was argued to be well described by the t - t' - t'' - J model [22]. As we show next, this is opposite to what we find for the $U_{dd} \rightarrow \infty$ limit of the three-band model. We predict qualitatively different dispersions for T-CuO and CuO₂, however their differences are hidden in magnetically twinned samples. We present our results next and then explain why they cannot be reproduced by one-band models.

Model: We study the $U_{dd} \rightarrow \infty$ limit of the Emery model, with spins at the Cu sites and a single doped hole on the O sublattice. This limit is justified because U_{dd} is the largest energy scale [23]. The corresponding Hamiltonian, see Fig. 1(b), is [17]:

$$\hat{H} = \hat{T}_{pp} + \hat{T}_{swap} + \hat{H}_{J_{pd}} + \hat{H}_{J_{dd}}. \quad (1)$$

$\hat{T}_{pp} = \sum_{i \neq j \in \text{O}, \sigma} t_{i-j} p_{i,\sigma}^\dagger p_{j,\sigma}$ describes next-nearest (nn) t_{pp} , and 2nd nn t'_{pp} hopping of the hole between ligand O $2p$ orbitals; the latter is restricted to oxygens bridged by a Cu. For technical details see the Supplemental Material [24] and Ref. [25]. \hat{T}_{swap} describes Cu-mediated hopping accompanied by a spin-swap. Specifically, the hole at a Cu site adjacent to the doped hole hops to another neighbor O, followed by the doped hole falling into the vacated Cu orbital. Because the original doped hole replaces the Cu hole, their spins are swapped. Thus $\hat{T}_{swap} = -t_{sw} \sum_{i \in \text{Cu}, \mathbf{u} \neq \mathbf{u}', \sigma, \sigma'} s_{\mathbf{u}-\mathbf{u}'} p_{i+\mathbf{u}, \sigma}^\dagger p_{i+\mathbf{u}', \sigma'} |i_{\sigma'}\rangle \langle i_{\sigma}|$, where $\mathbf{u}, \mathbf{u}' = (\pm 0.5, 0), (0, \pm 0.5)$ are the distances between Cu and its nn O sites. It shows the change of the Cu spin

located at \mathbf{R}_i from σ to σ' as the doped hole changes its spin from σ' to σ while moving to another O. The sign $s_{\eta} = \pm 1$ comes from overlaps of the orbitals involved [24]. $\hat{H}_{J_{pd}} = J_{pd} \sum_{i, \mathbf{u}} \mathbf{S}_i \cdot \mathbf{s}_{i+\mathbf{u}}$ is generated when the Cu hole hops onto the O hosting the doped hole, followed by one of the two holes returning to the Cu. This gives rise to AFM exchange between the spins $\mathbf{s}_{i+\mathbf{u}}$ of the doped hole and \mathbf{S}_i of its neighbor Cu. Finally, $\hat{H}_{J_{dd}} = J_{dd} \sum_{\langle i, j \rangle'} \mathbf{S}_i \cdot \mathbf{S}_j$ is the AFM coupling between nn Cu spins, except on the bond blocked by the doped hole. Its energy scale $J_{dd} \sim 150$ meV is taken as the unit of energy, in terms of which $t_{pp} = 4.1$, $t'_{pp} = 0.6t_{pp}$, $t_{sw} = 3.0$ and $J_{pd} = 2.8$ [23]. The Hubbard repulsion U_{pp} is not included in Eq. (1) because we consider only the case of a single doped hole.

In CuO₂ the ligand orbitals are the important ones, but it is straightforward to also include the in-plane non-ligand orbitals. These do not hybridize with Cu $3d_{x^2-y^2}$ so their addition does not affect \hat{T}_{swap} , $\hat{H}_{J_{pd}}$ or $\hat{H}_{J_{dd}}$, which arise from such hybridization. Only \hat{T}_{pp} must be supplemented accordingly. By symmetry, nn hopping between two non-ligand orbitals is the same t_{pp} as for ligand orbitals, with signs dictated by the lobes' overlap. Hopping between ligand and non-ligand orbitals, denoted \hat{T}_{mix} and shown by the arrow in Fig. 1(a), has magnitude $\tilde{t}_{pp}/t_{pp} = (t_{pp,\sigma} - t_{pp,\pi})/(t_{pp,\sigma} + t_{pp,\pi}) = 0.6$ because $t_{pp,\sigma} = 4t_{pp,\pi}$ [26]. For CuO₂, inclusion of the non-ligand orbitals has a minor effect on the qp dispersion [18].

The Hamiltonian for T-CuO is a straightforward generalization of Eq. (1). Hole hopping is described by the same $\hat{T}_{pp} + \hat{T}_{mix}$. Because of the two Cu sublattices, however, there are two sets of terms \hat{T}_{swap} , $\hat{H}_{J_{pd}}$ and $\hat{H}_{J_{dd}}$ which couple Cu spins on each sublattice to each other and to the doped hole, when it occupies a $2p$ orbital with ligand character for that sublattice. We use the same parameters for T-CuO like for CuO₂ (the results remain qualitatively similar if the parameters are varied within reasonable ranges) and focus on the effect of \hat{T}_{mix} , which moves the hole between the two sets of $2p$ orbitals and changes to which Cu sublattice it is coupled [21].

Variational approximation: We extract the qp dispersion $E_{qp}(\mathbf{k})$ from the one-hole propagator computed variationally in a restricted Hilbert space that allows up to n_m magnons to be created by the doped hole through \hat{T}_{swap} and $\hat{H}_{J_{pd}}$ processes, assuming that it was injected in a Néel-like background [18, 24]. Of course, in reality there are spin fluctuations in the AFM background, but because their energy scale J_{dd} is small, they are slow and have little effect on the qp : the hole creates and moves its magnon cloud on a timescale faster than that controlling the spin fluctuations, so the latter can be ignored [18, 19]. If the T-CuO energy scales are similar, and given the weak coupling between the two Cu sublattices, this approximation should remain valid.

In undoped T-CuO each Cu sublattice has AFM order due to its $\hat{H}_{J_{dd}}$ term. Any weak coupling \hat{J}_{dd} between the two Cu sublattices is therefore fully frustrated: any

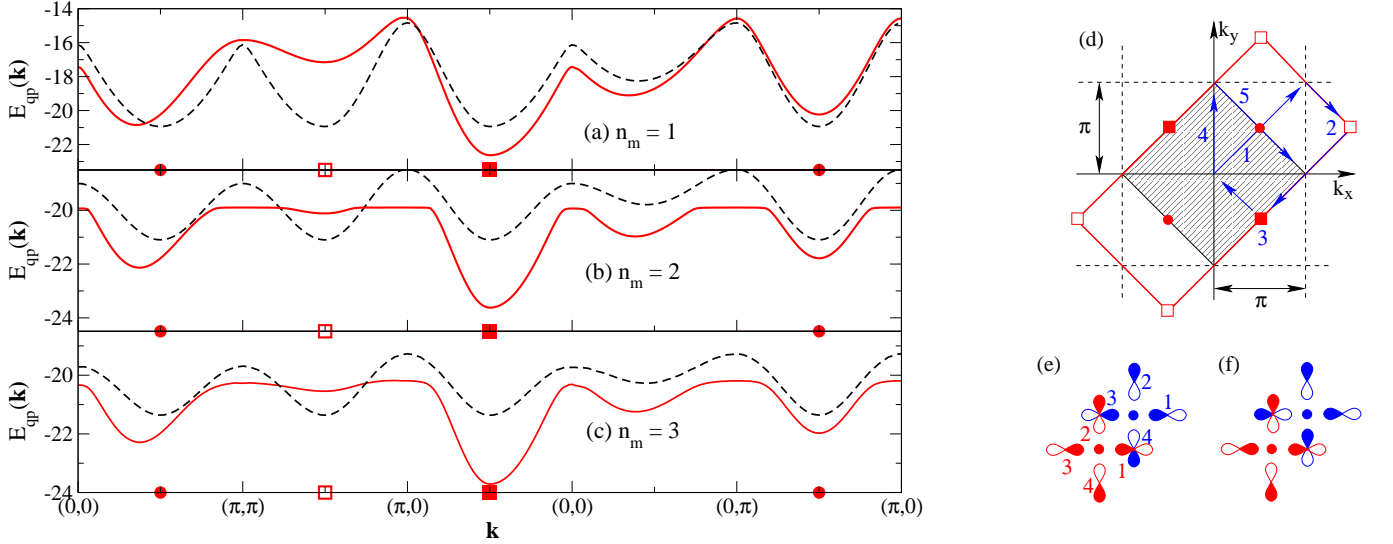


FIG. 2. (color online) Qp dispersion in units of J_{dd} for (a) $n_m = 1$, (b) $n_m = 2$, and (c) $n_m = 3$ with full/dashed lines for T-CuO/CuO₂. The Brillouin zone for the magnetic order of Fig. 1(c) is shown in red in (b). The shaded area is the smaller BZ for CuO₂. The points marked by circles and empty/full squares are equivalent in CuO₂ but not in T-CuO. (d) Hopping between two adjacent ZRSs, and (e) between a ZRS (red) and one with $x - y$ symmetry (blue). See text for more details.

spin interacts with equal numbers of up and down spins from the other sublattice. Nevertheless, order by disorder selects one of the two degenerate states depicted in Fig. 1(c), (d) as the ground-state of the undoped system [27]. Because they have FM chains running along the $x = \pm y$ diagonals, they are related by a C_4 rotation so it suffices to study one case. Thus for T-CuO in either of these states, the quasiparticle dispersion $E_{qp}(\mathbf{k})$ is not invariant to C_4 rotations, only to C_2 ones.

Results: Figures 2(a)-(c) show $E_{qp}(\mathbf{k})$ from the variational method with $n_m = 1, 2, 3$, respectively, for the magnetic order of Fig. 1(c). The Brillouin zone (BZ) is displayed in Fig. 2(d). Full/dashed lines are for T-CuO/CuO₂.

In CuO₂, at the points marked by circles and squares there are identical, nearly isotropic minima [10, 11]. With increasing n_m , the bandwidth narrows and the dispersion flattens below the polaron+one magnon continuum (both are standard polaronic effects [18]) but the shape is unchanged. The results are nearly converged at $n_m = 3$ for CuO₂, with a bandwidth of $\sim 2J_{dd}$ in agreement with exact diagonalization results and experimental data [18]).

In T-CuO, we verified that for $\hat{T}_{mix} = 0$ the same (but now doubly-degenerate) dispersion is obtained. When \hat{T}_{mix} is turned on, this degeneracy is lifted. Only the low-energy eigenenergy is shown in Fig. 2. Again, results are essentially converged for $n_m = 3$. As expected, the dispersion loses its invariance to C_4 rotations because the qp now moves in a magnetic background that lacks this symmetry. In the $k_x = -k_y$ quadrants $E_{qp}(\mathbf{k})$ again displays deep, isotropic minima around $\pm(\frac{\pi}{2}, -\frac{\pi}{2})$ (full squares) and is thus similar to CuO₂. The difference, however, is significant in the $k_x = k_y$ quadrants near the $\pm(\frac{\pi}{2}, \frac{\pi}{2})$ points (circles). Not only are energies here higher than

at the $\pm(\frac{\pi}{2}, -\frac{\pi}{2})$, but these minima are shifted toward the Γ point. Note that the BZ corners (empty squares) still mark local minima, but lying at high energies just below the polaron+one magnon continuum.

We now prove that this unusual dispersion for T-CuO involves physics beyond the Zhang-Rice singlet. As such, it cannot be described by one-band models obtained through a projection onto these states.

We start by estimating the effect of \hat{T}_{mix} on the CuO₂ degenerate eigenstates that appear in its absence, whose energy $E_0(\mathbf{k})$ is shown by dashed lines in Fig. 2. Especially near $(\pm\frac{\pi}{2}, \pm\frac{\pi}{2})$, the CuO₂ qp indeed has a large overlap with a ZRS Bloch state [19], and the hole occupies the $x^2 - y^2$ linear combination of O $2p$ ligand orbitals sketched for two nn sites in Fig. 2(e). For T-CuO, these degenerate states combine into one Bloch state $|d, \mathbf{k}\rangle$ with momentum \mathbf{k} in its bigger BZ. If we use $|d, \mathbf{k}\rangle$ as an approximation for the low-energy eigenstate, then the T-CuO dispersion becomes $E_{qp}(\mathbf{k}) \approx E_0(\mathbf{k}) + \delta E(\mathbf{k})$, where $\delta E(\mathbf{k}) = \langle d, \mathbf{k} | \hat{T}_{mix} | d, \mathbf{k} \rangle$ is:

$$\delta E(\mathbf{k}) = -\tilde{t}_{pp} \cos \frac{k_x + k_y}{2} [1 - \cos(k_x - k_y)].$$

The cosines are a geometric factor from the Bloch states' phase differences between neighboring Cu sites [24].

Because $\delta E(k_x = -k_y) = -2\tilde{t}_{pp} \sin^2 k_x$ and $\delta E(k_y = k_x \mp \pi) = -2\tilde{t}_{pp} \sin |k_x|$, minima at $\pm(\frac{\pi}{2}, -\frac{\pi}{2})$ (full squares) move to lower energies while minima at the BZ corners (empty squares) move up. This agrees with the results of Fig. 2.

However, because $\delta E(k_x = k_y) = 0$, the dispersion near $\pm(\frac{\pi}{2}, \frac{\pi}{2})$ (circles) should remain unchanged instead of these minima moving toward the Γ point. Moreover, we find that the overlap between the T-CuO qp and $|d, \mathbf{k}\rangle$

vanishes at $\mathbf{k} = \pm(\frac{\pi}{2}, \frac{\pi}{2})$. These facts clearly prove that the changes near the $\pm(\frac{\pi}{2}, \frac{\pi}{2})$ points cannot be due to Zhang-Rice singlet physics.

Indeed, \hat{T}_{mix} hopping between $x^2 - y^2$ linear combinations centred at nn Cu sites is suppressed, see Fig. 2(e): *eg.*, a hole at site 1 of the lower Cu (red) hops into $p_1^\dagger + p_3^\dagger$ of the upper Cu (blue), which is orthogonal to its $x^2 - y^2$ linear combination. Instead, hopping between adjacent $x^2 - y^2$ and $x - y$ combinations is enhanced, see Fig. 2(f). The shift of the $\pm(\frac{\pi}{2}, \frac{\pi}{2})$ minima toward Γ is due to a large mixing of the singlet with $x - y$ symmetry into the quasiparticle eigenstate, which thus loses its ZRS nature (for more details see the Supplemental Material [24]). Note that experiments like Refs. [28], which are sensitive only to the local singlet character, cannot distinguish a ZRS singlet from one with such mixed symmetry.

We checked that adding terms like \tilde{J}_{dd} and \tilde{J}_{pd} [21] has no qualitative effects on the dispersion. This is expected because their matrix elements are small and/or featureless near $(\pm\frac{\pi}{2}, \pm\frac{\pi}{2})$. We are therefore confident that our prediction is robust.

ARPES finds the T-CuO *qp* dispersion to obey C_4 symmetry and to have a large BZ, corresponding to a unit cell containing one Cu and one O atom [22]. Both features are very surprising for the long-range magnetic orders of Figs. 1(c), (d), which break the C_4 symmetry. Moreover, any AFM-type order has at least two magnetically non-equivalent Cu atoms so its BZ is like in Fig. 2(d) or smaller, never larger. Our results become consistent with ARPES if we assume the presence of domains in both ground-states, so that their average is measured experimentally. Indeed, as shown in the Supplemental Material

[24], averaging $E_{qp}(\mathbf{k})$ of Fig. 2(d) with its counterpart rotated by 90° leads to an apparent doubling of the BZ and a new pattern of minima with two different energies, in agreement with those found experimentally.

We predict that a dispersion like in Fig. 2 appears in the ARPES of “magnetically untwinned” T-CuO films in the insulating limit. This is very different and thus easily distinguishable from the one-band model prediction [22]. The observation of this pattern, with shallower displaced minima in two quadrants, will provide a clear proof of low-energy physics beyond the ZRS, and of the superiority of three-band models to model such materials. If T-CuO films can be doped, this new pattern of minima will open extraordinary opportunities to test many ideas relating the shape of the Fermi surface, location of “hot spots” and possibility of nesting, to much of the cuprate phenomenology, including the symmetry of the superconducting gap, formation of stripes, appearance and relevance of various other ordered phases, etc.

We note that ARPES measurements on untwinned pnictides have been successfully performed (see, *e.g.*, [29]). It is therefore reasonable to expect that similar measurements for T-CuO are feasible. An important lesson from this study is that low-energy physics of non-ZRS nature can arise in T-CuO and similar materials in suitable circumstances/symmetries. The presence of disorder, of other nearby quasiparticles, of stripes, charge-density wave or other ordered phases may have a similar effect in CuO₂ layers.

Acknowledgements: We thank G. Koster and M. Griener for useful discussions. Work was supported by NSERC, QMI, CIFAR, SNF, and a UBC 4Y Fellowship (CA).

-
- [1] J. G. Bednorz and K. A. Müller, Z. Phys. B **64**, 189 (1986).
 - [2] V. J. Emery, Phys. Rev. Lett. **58**, 2794 (1987).
 - [3] F.C. Zhang and T.M. Rice, Phys. Rev. B **37**, 3759 (1988).
 - [4] H. Eskes and G.A. Sawatzky, Phys. Rev. Lett. **61**, 1415 (1988).
 - [5] K. A. Chao, J. Spalek and A. M. Olés, J. Phys. C: Solid State Phys. **10**, L271 (1977); K. A. Chao, J. Spalek, and A. M. Oleś, Phys. Rev. B **18**, 3453 (1978); M. Ogata, and H. Shiba, J. Phys. Soc. Jpn. **57** 3074 (1988).
 - [6] A. I. Liechtenstein, M. I. Katsnelson, Phys. Rev. B. **62**, R9283(R) (2000)
 - [7] S. A. Trugman, Phys. Rev. B **37**, 1597 (1988).
 - [8] P. W. Leung and R. J. Gooding, Phys. Rev. B **52**, R15711 (1995); *ibid* Phys. Rev. B **54**, 711 (1996).
 - [9] P. W. Leung, B. O. Wells, and R. J. Gooding, Phys. Rev. B **56**, 6320 (1997).
 - [10] B. O. Wells, Z.-X. Shen, A. Matsuura, D. M. King, M. A. Kastner, M. Greven, and R. J. Birgeneau, Phys. Rev. Lett. **74**, 964 (1995).
 - [11] A. Damascelli, Z. Hussain, and Z.-X. Shen, Rev. Mod. Phys. **75**, 473 (2003).
 - [12] E. Pavarini, I. Dasgupta, T. Saha-Dasgupta, O. Jepsen, and O. K. Andersen, Phys. Rev. Lett. **87**, 047003 (2001); O.K. Andersen, A. I. Liechtenstein, O. Jepsen, and F. Paulsen, J. Phys. Chem. Solids, **56** 1573 (1995).
 - [13] H. Eskes and G. A. Sawatzky, Phys. Rev. B **44**, 9656 (1991).
 - [14] Surprisingly, a lot of this work discards the longer-range hopping terms despite their proven relevance.
 - [15] It is much more likely that the one-band models (with properly adjusted longer-range hopping) describe correctly the physics of the electron-doped side, because in this case the full O bands are inert spectators.
 - [16] M. Möller, G. A. Sawatzky and M. Berciu, Phys. Rev. Lett. **108**, 216403 (2012); *ibid*, Phys. Rev. B **86**, 075128 (2012).
 - [17] B. Lau, M. Berciu, and G. A. Sawatzky, Phys. Rev. Lett. **106**, 036401 (2011).
 - [18] H. Ebrahimnejad, G. A. Sawatzky, and M. Berciu, Nature Phys. **10**, 951 (2014).
 - [19] H. Ebrahimnejad, G. A. Sawatzky, and M. Berciu, cond-mat/1505.04405.
 - [20] W. Siemons, G. Koster, D.H.A. Blank, R.H. Hammond, T.H. Geballe, and M.R. Beasley, Phys. Rev. B **79**, 195122 (2009); D. Samal, H. Tan, Y. Takamura, W. Siemons, J. Verbeeck, G. Van Tendeloo, E. Arenholz, C.A. Jenkins, G. Rijnders, and G. Koster, Europhys. Lett. **105**, 17003

- (2014).
- [21] For completeness, we note that in Ref. [22] a small nn exchange $\tilde{J}_{dd} \sim 0.04$ was also included between Cu spins on the different sublattices. We have considered this term, as well as a weak \tilde{J}_{pd} coupling between the doped hole occupying a non-ligand orbital and its neighbor Cu spins (FM exchange is favored by Hund's coupling when the Cu hole hops into the O orbital orthogonal to that hosting the doped hole). None of these terms were found to lead to qualitative changes, and because of their relatively small magnitude, their quantitative effects are minor.
 - [22] S. Moser, L. Moreschini, H.-Y. Yang, D. Innocenti, F. Fuchs, N.H. Hansen, Y.J. Chang, K.S. Kim, A.L. Walter, A. Bostwick, E. Rotenberg, F. Mila, and M. Grioni, Phys. Rev. Lett. **113**, 187001 (2014).
 - [23] M. Ogata and H. Fukuyama, Rep. Prog. Phys **71**, 036501 (2008).
 - [24] See Supplemental Material at for more details.
 - [25] For complete technical details of the derivation of this effective Hamiltonian and further discussions of higher order terms, as well as a comparison with other work along similar lines, the reader is referred to the supplemental material of Ref. [17].
 - [26] W. A. Harrison, *Elementary Electronic Structure* (World Scientific, 1999).
 - [27] C.L. Henley, Phys. Rev. Lett. **62**, 2056 (1989); P. Chandra, P. Coleman, and A.I. Larkin, Phys. Rev. Lett. **64**, 88 (1990); C. Weber, L. Capriotti, G. Misguich, F. Becca, M. Elhajal, and F. Mila, Phys. Rev. Lett. **91**, 177202 (2003).
 - [28] L. H. Tjeng, B. Sinkovic, N. B. Brookes, J. B. Goedkoop, R. Hesper, E. Pellegrin, F. M. F. de Groot, S. Altieri, S. L. Hulbert, E. Shekel, and G. A. Sawatzky, Phys. Rev. Lett. **78**, 1126 (1997); N. B. Brookes, G. Ghiringhelli, O. Tjernberg, L. H. Tjeng, T. Mizokawa, T. W. Li, and A. A. Menovsky, Phys. Rev. Lett. **87**, 237003 (2001); N. B. Brookes, G. Ghiringhelli, A.-M. Charvet, A. Fujimori, T. Kakeshita, H. Eisaki, S. Uchida, and T. Mizokawa, Phys. Rev. Lett. **115**, 027002 (2015)
 - [29] M. Yi, D. Lu, J.-H. Chu, J. G. Analytis, A. P. Sorini, A. F. Kemper, B. Moritz, S.-K. Mo, R. G. Moore, M. Hashimoto, W.-S. Lee, Z. Hussain, T. P. Devereaux, I. R. Fisher, and Z.-X. Shen, Proc. Natl. Acad. Sci. **108** (17), 6878 (2011)